



# POLSKA NORMA

ICS 25.160.40

## PN-EN ISO 10675-2

**Wprowadza**

EN ISO 10675-2:2021, IDT

ISO 10675-2:2021, IDT

**Zastępuje**

PN-EN ISO 10675-2:2017-12

### Badania nieniszczące spoin

### Kryteria akceptacji badań radiograficznych

### Część 2: Aluminium i jego stopy

Norma Europejska EN ISO 10675-2:2021 *Non-destructive testing of welds -- Acceptance levels for radiographic testing -- Part 2: Aluminium and its alloys (ISO 10675-2:2021)* ma status **Polskiej Normy**

**PN-EN ISO 10675-2:2022-05**

## **Przedmowa krajowa**

Niniejsza norma została zatwierdzona przez Prezesa PKN 26 kwietnia 2022 r.

Komitetem krajowym odpowiedzialnym za normę jest PKN/KT 165 ds. Spawania i Procesów Pokrewnych.

Istnieje możliwość przetłumaczenia normy na język polski na wniosek zainteresowanych środowisk. Decyzję podejmuje właściwy Komitet Techniczny.

Niniejsza norma zastępuje: PN-EN ISO 10675-2:2017-12.

Odpowiedniki krajowe norm i innych dokumentów powołanych w niniejszym dokumencie można znaleźć w katalogu Polskich Norm. Oryginały norm i innych dokumentów powołanych są dostępne w PKN.

W sprawach merytorycznych dotyczących treści normy można zwracać się do właściwego Komitetu Technicznego lub właściwej Rady Sektorowej PKN, kontakt: [www.pkn.pl](http://www.pkn.pl).

## **Nota uznaniowa**

Norma Europejska EN ISO 10675-2:2021 została uznana przez PKN za Polską Normę PN-EN ISO 10675-2:2022-05.

EUROPEAN STANDARD

**EN ISO 10675-2**

NORME EUROPÉENNE

EUROPÄISCHE NORM

December 2021

ICS 25.160.40

Supersedes EN ISO 10675-2:2017

English Version

**Non-destructive testing of welds - Acceptance levels for  
radiographic testing - Part 2: Aluminium and its alloys (ISO  
10675-2:2021)**

Essais non destructifs des assemblages soudés -  
Niveaux d'acceptation pour l'évaluation par  
radiographie - Partie 2: Aluminium et ses alliages (ISO  
10675-2:2021)

Zerstörungsfreie Prüfung von Schweißverbindungen -  
Zulässigkeitsgrenzen für die Durchstrahlungsprüfung -  
Teil 2: Aluminium und seine Legierungen (ISO 10675-  
2:2021)

This European Standard was approved by CEN on 5 December 2021.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels**

**EN ISO 10675-2:2021 (E)**

| <b>Contents</b>               | <b>Page</b> |
|-------------------------------|-------------|
| <b>European foreword.....</b> | <b>3</b>    |

## **European foreword**

This document (EN ISO 10675-2:2021) has been prepared by Technical Committee ISO/TC 44 "Welding and allied processes" in collaboration with Technical Committee CEN/TC 121 "Welding and allied processes" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2022, and conflicting national standards shall be withdrawn at the latest by June 2022.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 10675-2:2017.

Any feedback and questions on this document should be directed to the users' national standards body/national committee. A complete listing of these bodies can be found on the CEN website.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

## **Endorsement notice**

The text of ISO 10675-2:2021 has been approved by CEN as EN ISO 10675-2:2021 without any modification.



# INTERNATIONAL STANDARD

# ISO 10675-2

Third edition  
2021-12

Corrected version  
2022-02

---

---

## Non-destructive testing of welds — Acceptance levels for radiographic testing —

### Part 2: Aluminium and its alloys

*Essais non destructifs des assemblages soudés — Niveaux  
d'acceptation pour évaluation par radiographie —*

*Partie 2: Aluminium et ses alliages*



Reference number  
ISO 10675-2:2021(E)

© ISO 2021

## ISO 10675-2:2021(E)



### **COPYRIGHT PROTECTED DOCUMENT**

© ISO 2021

All rights reserved. Unless otherwise specified, or required in the context of its implementation, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office  
CP 401 • Ch. de Blandonnet 8  
CH-1214 Vernier, Geneva  
Phone: +41 22 749 01 11  
Email: [copyright@iso.org](mailto:copyright@iso.org)  
Website: [www.iso.org](http://www.iso.org)

Published in Switzerland

# Contents

Page

|   |           |
|---|-----------|
| <b>Foreword</b> .....   | <b>iv</b> |
| <b>1 Scope</b> .....  | <b>1</b>  |
| <b>2 Normative references</b> .....   | <b>1</b>  |
| <b>3 Terms and definitions</b> .....  | <b>1</b>  |
| <b>4 Symbols and abbreviations</b> .....  | <b>1</b>  |
| <b>5 Radiographic technique</b> .....   | <b>2</b>  |
| <b>6 General</b> .....  | <b>2</b>  |
| <b>7 Acceptance levels</b> .....  | <b>3</b>  |
| <b>Annex A (informative) Guidance to the limitations of radiographic testing</b> .....                | <b>6</b>  |
| <b>Annex B (informative) Examples for determination of area percentage (%) of imperfections</b> ..... | <b>7</b>  |
| <b>Annex C (informative) Calculation of the sum of acceptable areas</b> .....                         | <b>9</b>  |
| <b>Bibliography</b> .....   | <b>14</b> |

## ISO 10675-2:2021(E)

### Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see [www.iso.org/iso/foreword.html](http://www.iso.org/iso/foreword.html).

This document was prepared by Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 5, *Testing and inspection of welds*, in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 121, *Welding and allied processes*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This third edition cancels and replaces the second edition (ISO 10675-2:2017), which has been technically revised.

The main changes compared to the previous edition are as follows:

- new [Table 1](#) added with abbreviations;
- in [Table 4](#) (former [Table 3](#)), acceptance levels for maximum permissible pore sizes of porosity, clustered porosity, linear porosity, elongated cavities and for lack of fusion have been added;
- the acceptance levels in [Clause 6](#) have been extended (General and tables);
- the capture of [Figure B.1](#) has been revised to conform with ISO 10042:2018;
- [Figures C.1, C.2](#) and the text have been revised to conform with ISO 10042:2018.
- the document has been editorially revised.

A list of all parts of the ISO 10675 series can be found on the ISO website.

Official interpretations of ISO/TC 44 documents, where they exist, are available from this page: <https://committee.iso.org/sites/tc44/home/interpretation.html>.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at [www.iso.org/members.html](http://www.iso.org/members.html).

This corrected version of ISO 10675-2:2021 incorporates the following correction:

- in [Table 4](#), line number 8 of the column "Acceptance level 3", the formula shall be corrected as follows:

*" $l \leq 0,3s$ , max. 3 mm"*



# Non-destructive testing of welds — Acceptance levels for radiographic testing —

## Part 2: Aluminium and its alloys

### 1 Scope

This document specifies acceptance levels for indications from imperfections in aluminium butt welds detected by radiographic testing. If agreed, the acceptance levels can be applied to other types of welds (such as fillet welds etc.) or materials.

The acceptance levels can be related to welding standards, application standards, specifications or codes. This document assumes that the radiographic testing has been carried out in accordance with ISO 17636-1 for RT-F (F = film) or ISO 17636-2 for RT-S (S = radioscopy) and RT-D (D = digital detectors).

### 2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6520-1, *Welding and allied processes — Classification of geometric imperfections in metallic materials — Part 1: Fusion welding*

ISO 10042, *Welding — Arc-welded joints in aluminium and its alloys — Quality levels for imperfections*

ISO 17636-1, *Non-destructive testing of welds — Radiographic testing — Part 1: X- and gamma-ray techniques with film*

ISO 17636-2, *Non-destructive testing of welds — Radiographic testing — Part 2: X- and gamma-ray techniques with digital detectors*

ISO 17637, *Non-destructive testing of welds — Visual testing of fusion-welded joints*

### 3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <https://www.electropedia.org/>

### 4 Symbols and abbreviations

For the purposes of this document, the symbols given in [Table 1](#) apply.

## ISO 10675-2:2021(E)

Table 1 — Symbols

|            |  |
|------------|--|
| $A$        | is the sum of projected areas of indications related to each $L \times w_p$ in percentage (see <a href="#">Annex B</a> )             |
| $b$        | is the width of excess penetration of weld, in millimetres   |
| $D$        | is the distance between indications  |
| $d$        | is the diameter of pore, in millimetres  |
| $d_A$      | is the diameter of area surrounding a group of gas holes (e.g. clustered porosity), in millimetres                                   |
| $h$        | is the width of indication, the width or height of surface or cross surface imperfection, in millimetres                             |
| $l$        | is the length of indication, in millimetres (see also <a href="#">Figure C.3</a> and <a href="#">Figure C.4</a> for linear porosity) |
| $L$        | is any 100 mm testing length, in millimetres (equivalent to $l_p$ in ISO 10042)  |
| $s$        | is the nominal butt weld thickness, in millimetres (see also ISO 2553)   |
| $t$        | is the material thickness, in millimetres  |
| $w_p$      | is the width of the weld, in millimetres   |
| $\Sigma l$ | is the summary length of imperfections within $L$ (indications shall not be divided into different ranges $L$ )                      |

## 5 Radiographic technique

Depending on the weld quality level, radiographic techniques class A or class B in accordance with ISO 17636-1 shall be used for RT-F as shown in [Table 2](#) and radiographic techniques class A or class B in accordance with ISO 17636-2 shall be used for RT-S or RT-D as shown in [Table 3](#).

Table 2 — Radiographic testing with film (RT-F)

| Quality levels in accordance with ISO 10042 | Testing techniques and classes in accordance with ISO 17636-1 for RT-F | Acceptance levels in accordance with this document |
|---|--|--|
| B   | B  | 1  |
| C   | B <sup>a</sup>   | 2  |
| D   | A  | 3  |

<sup>a</sup> However, the minimum number of exposures for circumferential weld testing can correspond to the requirements of class A of ISO 17636-1.

Table 3 — Radiographic testing with radioscopy (RT-S) and radiographic testing with digital detectors (RT-D)

| Quality levels in accordance with ISO 10042 | Testing techniques and classes in accordance with ISO 17636-2 for RT-S and RT-D | Acceptance levels in accordance with this document |
|---|---|--|
| B   | B   | 1  |
| C   | B <sup>a</sup>  | 2  |
| D   | A   | 3  |

<sup>a</sup> However, the minimum number of exposures for circumferential weld testing can correspond to the requirements of class A of ISO 17636-2.

## 6 General

Accessible areas of welded joints shall be visually tested in accordance with ISO 17637 and evaluated before radiographic testing. ISO 17635 provides information on the NDT for testing and evaluation of fusion welds in metallic materials.

The acceptance levels of this document are basically valid for evaluation of imperfections which cannot be detected and evaluated by visual testing (see [Table 4](#)). Surface imperfections (see [Table 5](#); such as undercut and excessive penetration, surface damage, weld spatter, etc.) which cannot be evaluated by

visual testing due to object geometry, but where the interpreter suspects that the ISO 10042 quality levels are not fulfilled, shall be subject to more specific testing for quantification.

When quantification of undercut and/or excessive penetration by radiographic testing is required, specific procedures using test exposures may be applied in order to establish a basis for approximate quantification in accordance with the requirements of ISO 10042. This shall be specified in the adopted specification/procedure.

When assessing whether a weld meets the requirements specified for a weld quality level, the sizes of imperfections permitted by this document are compared with the dimensions of indications revealed by a radiograph made of the weld.

## 7 Acceptance levels

The acceptance levels for indications are shown in [Table 4](#) and [Table 5](#). The types of imperfections are selected from ISO 10042 and specified in ISO 6520-1 (see [Annex A](#)).

Any two adjacent imperfections separated by a distance smaller than the major dimension of the smaller imperfection shall be considered as a single imperfection (see [Annex C](#)).

[Annex B](#) supports the visual evaluation of porosity.

Indications shall not be divided into different ranges,  $L$ .

**Table 4 — Acceptance levels for internal indications in butt welds**

| No.            | Type of internal imperfections in accordance with ISO 6520-1 | Acceptance level 3 <sup>a</sup>  | Acceptance level 2 <sup>a</sup>  | Acceptance level 1   |
|----------------|--|--|--|--|
| 1              | Cracks (100)   | Not permitted  | Not permitted  | Not permitted  |
| 2a             | Gas pores (2011)   | $d \leq 0,4s$ , max. 6 mm  | $d \leq 0,3s$ , max. 5 mm  | $d \leq 0,2s$ , max. 4 mm  |
| 2b             | Porosity (2012)<br>material thickness 0,5 mm to 3 mm         | $d \leq 0,4s$ , max. 6 mm<br>$A \leq 6\%$<br>$L = 100$ mm                | $d \leq 0,3s$ , max. 5 mm<br>$A \leq 2\%$<br>$L = 100$ mm                | $d \leq 0,2s$ , max. 4 mm<br>$A \leq 1\%$<br>$L = 100$ mm                  |
| 2c             | Porosity (2012)<br>material thickness >3 mm to 12 mm         | $d \leq 0,4s$ , max. 6 mm<br>$A \leq 10\%$<br>$L = 100$ mm               | $d \leq 0,3s$ , max. 5 mm<br>$A \leq 4\%$<br>$L = 100$ mm                | $d \leq 0,2s$ , max. 4 mm<br>$A \leq 2\%$<br>$L = 100$ mm                  |
| 2d             | Porosity (2012)<br>material thickness >12 mm to 30 mm        | $d \leq 0,4s$ , max. 6 mm<br>$A \leq 15\%$<br>$L = 100$ mm               | $d \leq 0,3s$ , max. 5 mm<br>$A \leq 6\%$<br>$L = 100$ mm                | $d \leq 0,2s$ , max. 4 mm<br>$A \leq 3\%$<br>$L = 100$ mm                  |
| 2e             | Porosity (2012)<br>material thickness >30 mm                 | $d \leq 0,4s$ , max. 6 mm<br>$A \leq 20\%$<br>$L = 100$ mm               | $d \leq 0,3s$ , max. 5 mm<br>$A \leq 8\%$<br>$L = 100$ mm                | $d \leq 0,2s$ , max. 4 mm<br>$A \leq 4\%$<br>$L = 100$ mm                  |
| 3 <sup>b</sup> | Clustered (localized) porosity (2013)                        | $d_A \leq 25$ mm or<br>$d_{A,max} \leq w_p$<br>$d \leq 0,4s$ , max. 6 mm | $d_A \leq 20$ mm or<br>$d_{A,max} \leq w_p$<br>$d \leq 0,3s$ , max. 5 mm | $d_A \leq 15$ mm or<br>$d_{A,max} \leq w_p/2$<br>$d \leq 0,2s$ , max. 4 mm |

<sup>a</sup> Acceptance levels 3 and 2 may be specified with suffix X which denotes that all indications over 25 mm are unacceptable.

<sup>b</sup> See [Figure C.1](#) and [Figure C.2](#).

<sup>c</sup> See [Figure C.3](#) and [Figure C.4](#).

<sup>d</sup> See [Figure C.5](#) and [Figure C.6](#).

<sup>e</sup> If the length of the weld is below 100 mm, the maximum length of indications shall not exceed 25 % of that weld length.

## ISO 10675-2:2021(E)

Table 4 (continued)

| No.             | Type of internal imperfections in accordance with ISO 6520-1 | Acceptance level 3 <sup>a</sup>  | Acceptance level 2 <sup>a</sup>  | Acceptance level 1          |
|-----------------|--|--|--|-----------------------------|
| 4 <sup>ce</sup> | Linear porosity (2014)                                       | $l \leq 25$ mm<br>$d \leq 0,4s$ , max. 6 mm<br>$L = 100$ mm  | Not permitted  | Not permitted               |
| 5 <sup>d</sup>  | Elongated cavities (2015) and wormholes (2016)               | $l \leq 0,4s$ , max. 6 mm  | $l < 0,3s$ , max. 4 mm   | $l < 0,2s$ , max. 3 mm      |
| 6               | Oxide inclusion (303)  | $\sum l < s$ , max. 10 mm  | $\sum l < 0,5s$ , max. 5 mm  | $\sum l < 0,2s$ , max. 3 mm |
| 7               | Tungsten inclusions (3041)                                   | $l < 0,4s$ , max. 6 mm   | $l < 0,3s$ , max. 4 mm   | $l < 0,2s$ , max. 3 mm      |
| 8 <sup>e</sup>  | Lack of fusion (401)   | Not breaking the surface<br>$l \leq 0,3s$ , max. 3 mm<br>Only intermittently and not breaking the surface $\sum l \leq 25$ mm,<br>$L = 100$ mm | Not permitted  | Not permitted               |
| 9 <sup>e</sup>  | Lack of penetration (402)                                    | $\sum l < 25$ mm,<br>$L = 100$ mm  | Permitted provided welded from both sides and not breaking the surface<br>$\sum l \leq 25$ mm,<br>$L = 100$ mm | Not permitted               |

<sup>a</sup> Acceptance levels 3 and 2 may be specified with suffix X which denotes that all indications over 25 mm are unacceptable.

<sup>b</sup> See [Figure C.1](#) and [Figure C.2](#).

<sup>c</sup> See [Figure C.3](#) and [Figure C.4](#).

<sup>d</sup> See [Figure C.5](#) and [Figure C.6](#).

<sup>e</sup> If the length of the weld is below 100 mm, the maximum length of indications shall not exceed 25 % of that weld length.

Table 5 — Acceptance levels for surface imperfections

| No.              | Type of surface imperfections in accordance with ISO 6520-1 | Acceptance level 3 <sup>a</sup>  | Acceptance level 2 <sup>a</sup>  | Acceptance level 1   |
|------------------|---|--|--|--|
| 10               | Crater cracks (104)   | $l \leq 0,4s$  | Not permitted  | Not permitted  |
| 11a              | Continuous undercut (5011)                                  | Smooth transition is required<br>$h \leq 0,2t$ , max. 1 mm                     | Smooth transition is required<br>$h \leq 0,1t$ , max. 0,5 mm                 | Not permitted  |
| 11b <sup>b</sup> | Intermittent undercut (5012)                                | Smooth transition is required<br>$h \leq 0,2t$ , max. 1,5 mm<br>$l \leq 25$ mm | Smooth transition is required<br>$h \leq 0,1t$ , max. 1 mm<br>$l \leq 25$ mm | Smooth transition is required<br>$h \leq 0,1t$ , max. 0,5 mm<br>$l \leq 25$ mm |
| 12               | Excess penetration (504)                                    | $h \leq 5$ mm  | $h \leq 4$ mm  | $h \leq 3$ mm  |

NOTE The acceptance levels are those specified for visual testing. These imperfections are normally evaluated by visual testing.

<sup>a</sup> Acceptance levels 3 and 2 can be specified with suffix X which denotes that all indications over 25 mm are unacceptable.

<sup>b</sup> If the length of the weld is below 100 mm, the maximum length of indications shall not exceed 25 % of that weld length.

Table 5 (continued)

| No.   | Type of surface imperfections in accordance with ISO 6520-1 | Acceptance level 3 <sup>a</sup>               | Acceptance level 2 <sup>a</sup>             | Acceptance level 1                             |
|---|---|---|---|--|
| 13 <sup>b</sup>   | Root concavity (515)  | $l \leq 25$ mm<br>$h \leq 0,2t$ , max. 1,5 mm | $l \leq 25$ mm<br>$h \leq 0,1t$ , max. 1 mm | $l \leq 25$ mm<br>$h \leq 0,05t$ , max. 0,5 mm |
| 14 <sup>b</sup>   | Shrinkage groove (5013)                                     | $l \leq 25$ mm<br>$h \leq 0,2t$ , max. 1,5 mm | $l \leq 25$ mm<br>$h \leq 0,1t$ , max. 1 mm | $l \leq 25$ mm<br>$h \leq 0,05t$ , max. 0,5 mm |
| NOTE The acceptance levels are those specified for visual testing. These imperfections are normally evaluated by visual testing.      |   |   |   |  |
| <sup>a</sup> Acceptance levels 3 and 2 can be specified with suffix X which denotes that all indications over 25 mm are unacceptable. |   |   |   |  |
| <sup>b</sup> If the length of the weld is below 100 mm, the maximum length of indications shall not exceed 25 % of that weld length.  |   |   |   |  |

## Annex A (informative)

### Guidance to the limitations of radiographic testing

#### A.1 General

The numbers between brackets conform to those used in ISO 6520-1.

#### A.2 Volumetric imperfections in butt welds

- Porosities and gas pores (2011, 2012, 2013, 2014 and 2017)
- Wormholes and elongated cavities (2016 and 2015)
- Oxide inclusions (303)
- Tungsten inclusions (3041)

The above imperfections listed in [Table 4](#) and [5](#) are readily detected using radiographic techniques class A or class B of ISO 17636-1 for RT-F as shown in [Table 2](#), or ISO 17636-2 for RT-S or RT-D as shown in [Table 3](#).

#### A.3 Cracks in butt welds

- Crater cracks (104)
- Cracks (100)

The detectability of cracks by radiographic testing depends on the crack height, the ramification (presence of branching parts), opening width, direction of the X-ray beam to crack orientation and radiographic technique parameters.

Reliable detection of all cracks is therefore limited. The use of radiographic techniques class B or better, as specified in ISO 17636-1 and ISO 17636-2, provides better crack detectability than radiographic techniques class A.

#### A.4 Planar imperfections in butt welds

- Lack of fusion (401)
- Lack of penetration (402)

The detection of lack of fusion and lack of penetration depends on characteristics of imperfections and radiographic technique parameters.

Lack of side wall fusion is probably not be detected (except it is associated with other imperfections such as slag inclusions) unless it is radiographed in direction of the side wall.

## Annex B (informative)

### Examples for determination of area percentage (%) of imperfections

[Figure B.1](#) to [Figure B.10](#) give a presentation of different area percentage (%) of imperfections in an area of 60 mm × 20 mm. This should assist the assessment of imperfections on radiographs.

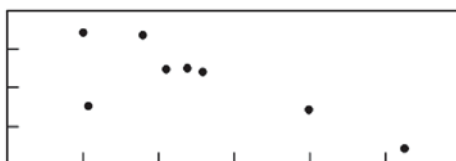


Figure B.1 —  $A = 0,5 \%$ ,  $d = 1 \text{ mm}$ , 8 pores

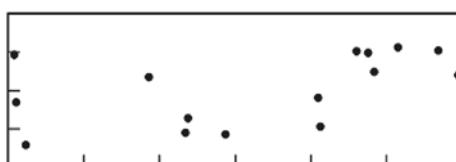


Figure B.2 —  $A = 1 \%$ ,  $d = 1 \text{ mm}$ , 15 pores

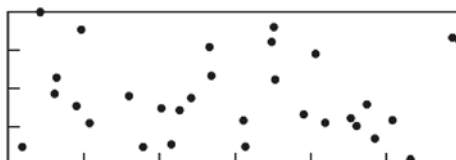


Figure B.3 —  $A = 2 \%$ ,  $d = 1 \text{ mm}$ , 31 pores

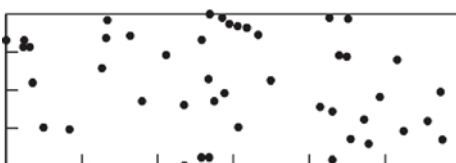


Figure B.4 —  $A = 3 \%$ ,  $d = 1 \text{ mm}$ , 45 pores

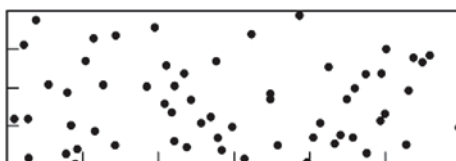


Figure B.5 —  $A = 4 \%$ ,  $d = 1 \text{ mm}$ , 61 pores

ISO 10675-2:2021(E)

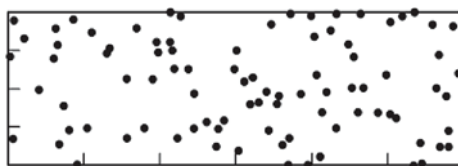


Figure B.6 —  $A = 6\%$ ,  $d = 1\text{ mm}$ , 92 pores

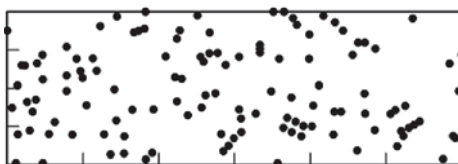


Figure B.7 —  $A = 8\%$ ,  $d = 1\text{ mm}$ , 122 pores

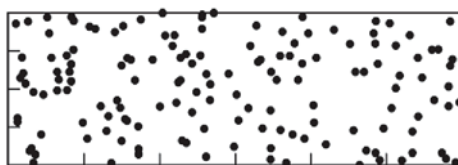


Figure B.8 —  $A = 10\%$ ,  $d = 1\text{ mm}$ , 153 pores

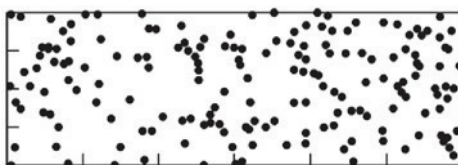


Figure B.9 —  $A = 15\%$ ,  $d = 1\text{ mm}$ , 229 pores

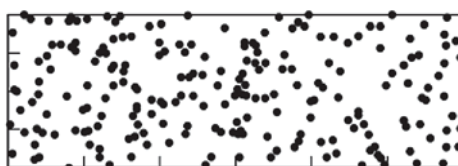



Figure B.10 —  $A = 20\%$ ,  $d = 1\text{ mm}$ , 305 pores

NOTE [Figures B.1](#) to B.10 correspond to ISO 10042:2018, Figures A.1 to A.10. The figures have been generated with a random generator for the pore position and sometimes pores overlap, resulting in fewer countable pores than expected.

## Annex C (informative)

### Calculation of the sum of acceptable areas

#### C.1 Clustered porosity

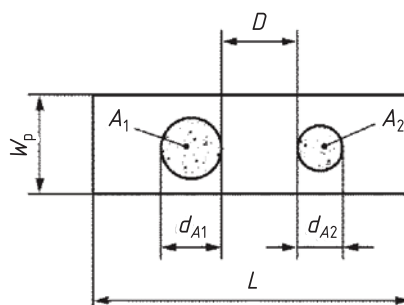


#### Key

- $A_1$  area of clustered porosity indication 1
- $A_2$  area of clustered porosity indication 2
- $d_{A1}$  diameter of  $A_1$
- $d_{A2}$  diameter of  $A_2$
- $D$  distance between indications
- $L$  any 100 mm testing length
- $w_p$  width of the weld

Figure C.1 — Clustered porosity,  $D \geq d_{A2}$

## ISO 10675-2:2021(E)

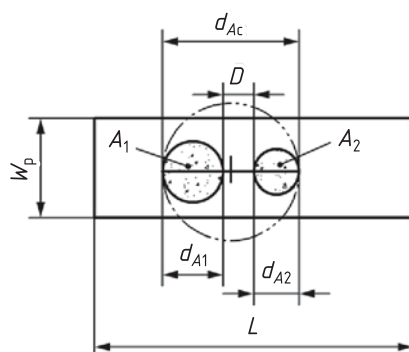**Key**

- $A_1$  area of clustered porosity indication 1
- $A_2$  area of clustered porosity indication 2
- $d_{A1}$  diameter of  $A_1$
- $d_{A2}$  diameter of  $A_2$
- $d_{Ac}$  diameter of circle, surrounding all gas pores
- $D$  distance between indications
- $L$  any 100 mm testing length
- $w_p$  width of the weld

**Figure C.2 — Clustered porosity,  $D < d_{A2}$**


The total gas pore area within the cluster is represented by a circle of diameter,  $d_A$ , surrounding all the gas pores.

The requirement for a single gas pore shall be met by all the gas pores within this circle. A permitted porous area shall be local. The possibility of the pore cluster masking other imperfections shall be taken into consideration.


If  $D$  is less than  $d_{A1}$  or  $d_{A2}$ , whichever is smaller, then the total gas pore area is represented by a circle of diameter  $d_{Ac}$ , where  $d_{Ac} = d_{A1} + d_{A2} + D$ .

Systematic clustered porosity is not permitted.  $d_A$  corresponds to  $d_{A1}$ ,  $d_{A2}$  or  $d_{Ac}$ , whichever is applicable.

## C.2 Linear porosity and gas holes (pores)

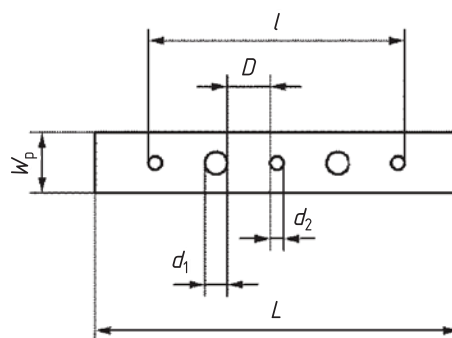**Key**

- $d_1$  diameter of pore indication 1
- $d_2$  diameter of pore indication 2
- $D$  distance between indications
- $l$  length of indication
- $L$  any 100 mm testing length
- $w_p$  width of the weld

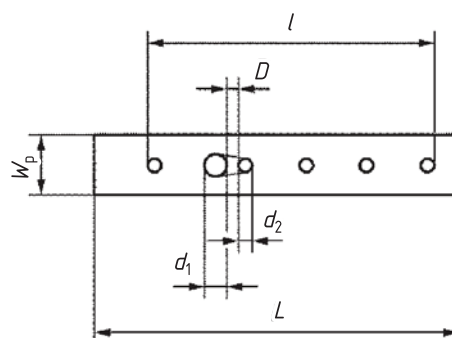**Figure C.3 — Linear porosity and gas holes (pores),  $D \geq d_2$** **Key**

- $d_1$  diameter of pore indication 1
- $d_2$  diameter of pore indication 2
- $D$  distance between indications
- $l$  length of indication
- $L$  any 100 mm testing length
- $w_p$  width of the weld


**Figure C.4 — Linear porosity and gas holes (pores),  $D < d_2$** 

The sum of the different pore areas related to the evaluation area,  $L \times w_p$  (Figure C.3) shall be calculated.

If  $D$  is smaller than the smaller diameter of one of the neighbouring pores, the full connected area of the two pores is to be taken into the sum of imperfections (Figure C.4).


## ISO 10675-2:2021(E)

## C.3 Elongated cavities and wormholes

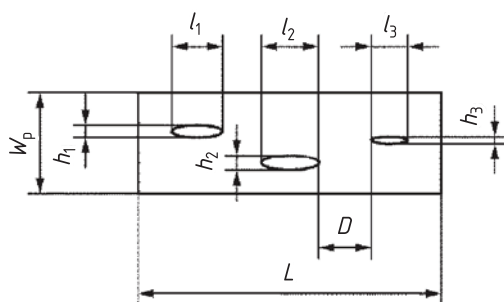

## Key

- $l_1$  length of cavity indication 1
- $l_2$  length of cavity indication 2
- $l_3$  length of cavity indication 3
- $h_1$  height of cavity indication 1
- $h_2$  height of cavity indication 2
- $h_3$  height of cavity indication 3
- $D$  distance between indications
- $L$  any 100 mm testing length
- $w_p$  width of the weld

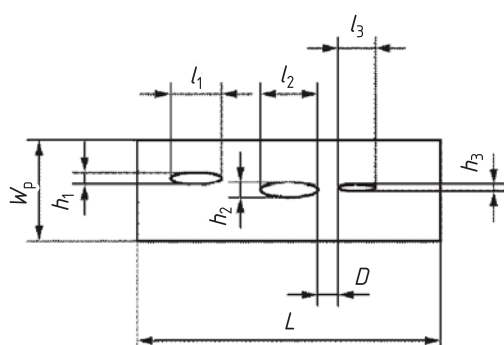Figure C.5 — Elongated cavities and wormholes,  $D \geq l_3$ 

## Key

- $l_1$  length of cavity indication 1
- $l_2$  length of cavity indication 2
- $l_3$  length of cavity indication 3
- $h_1$  height of cavity indication 1
- $h_2$  height of cavity indication 2
- $h_3$  height of cavity indication 3
- $D$  distance between indications
- $L$  any 100 mm testing length
- $w_p$  width of the weld

Figure C.6 — Elongated cavities and wormholes,  $D < l_3$ 

The sum of the length of indications,  $\sum l$ , shall be determined for each testing length,  $L$  (Figure C.5).

If  $D$  is smaller than the shorter length of one of the neighbouring imperfections, the full connection of the two imperfections is to be taken into the sum of imperfections ([Figure C.6](#)).

## **Bibliography**

- [1] ISO 2553, *Welding and allied processes — Symbolic representation on drawings — Welded joints*
- [2] ISO 17635, *Non-destructive testing of welds — General rules for metallic materials*



## ISO 10675-2:2021(E)

---

---

**ICS 25.160.40**

Price based on 14 pages

© ISO 2021 – All rights reserved